


2-Coat, 1 Day Oil-Based Wood Floor Program

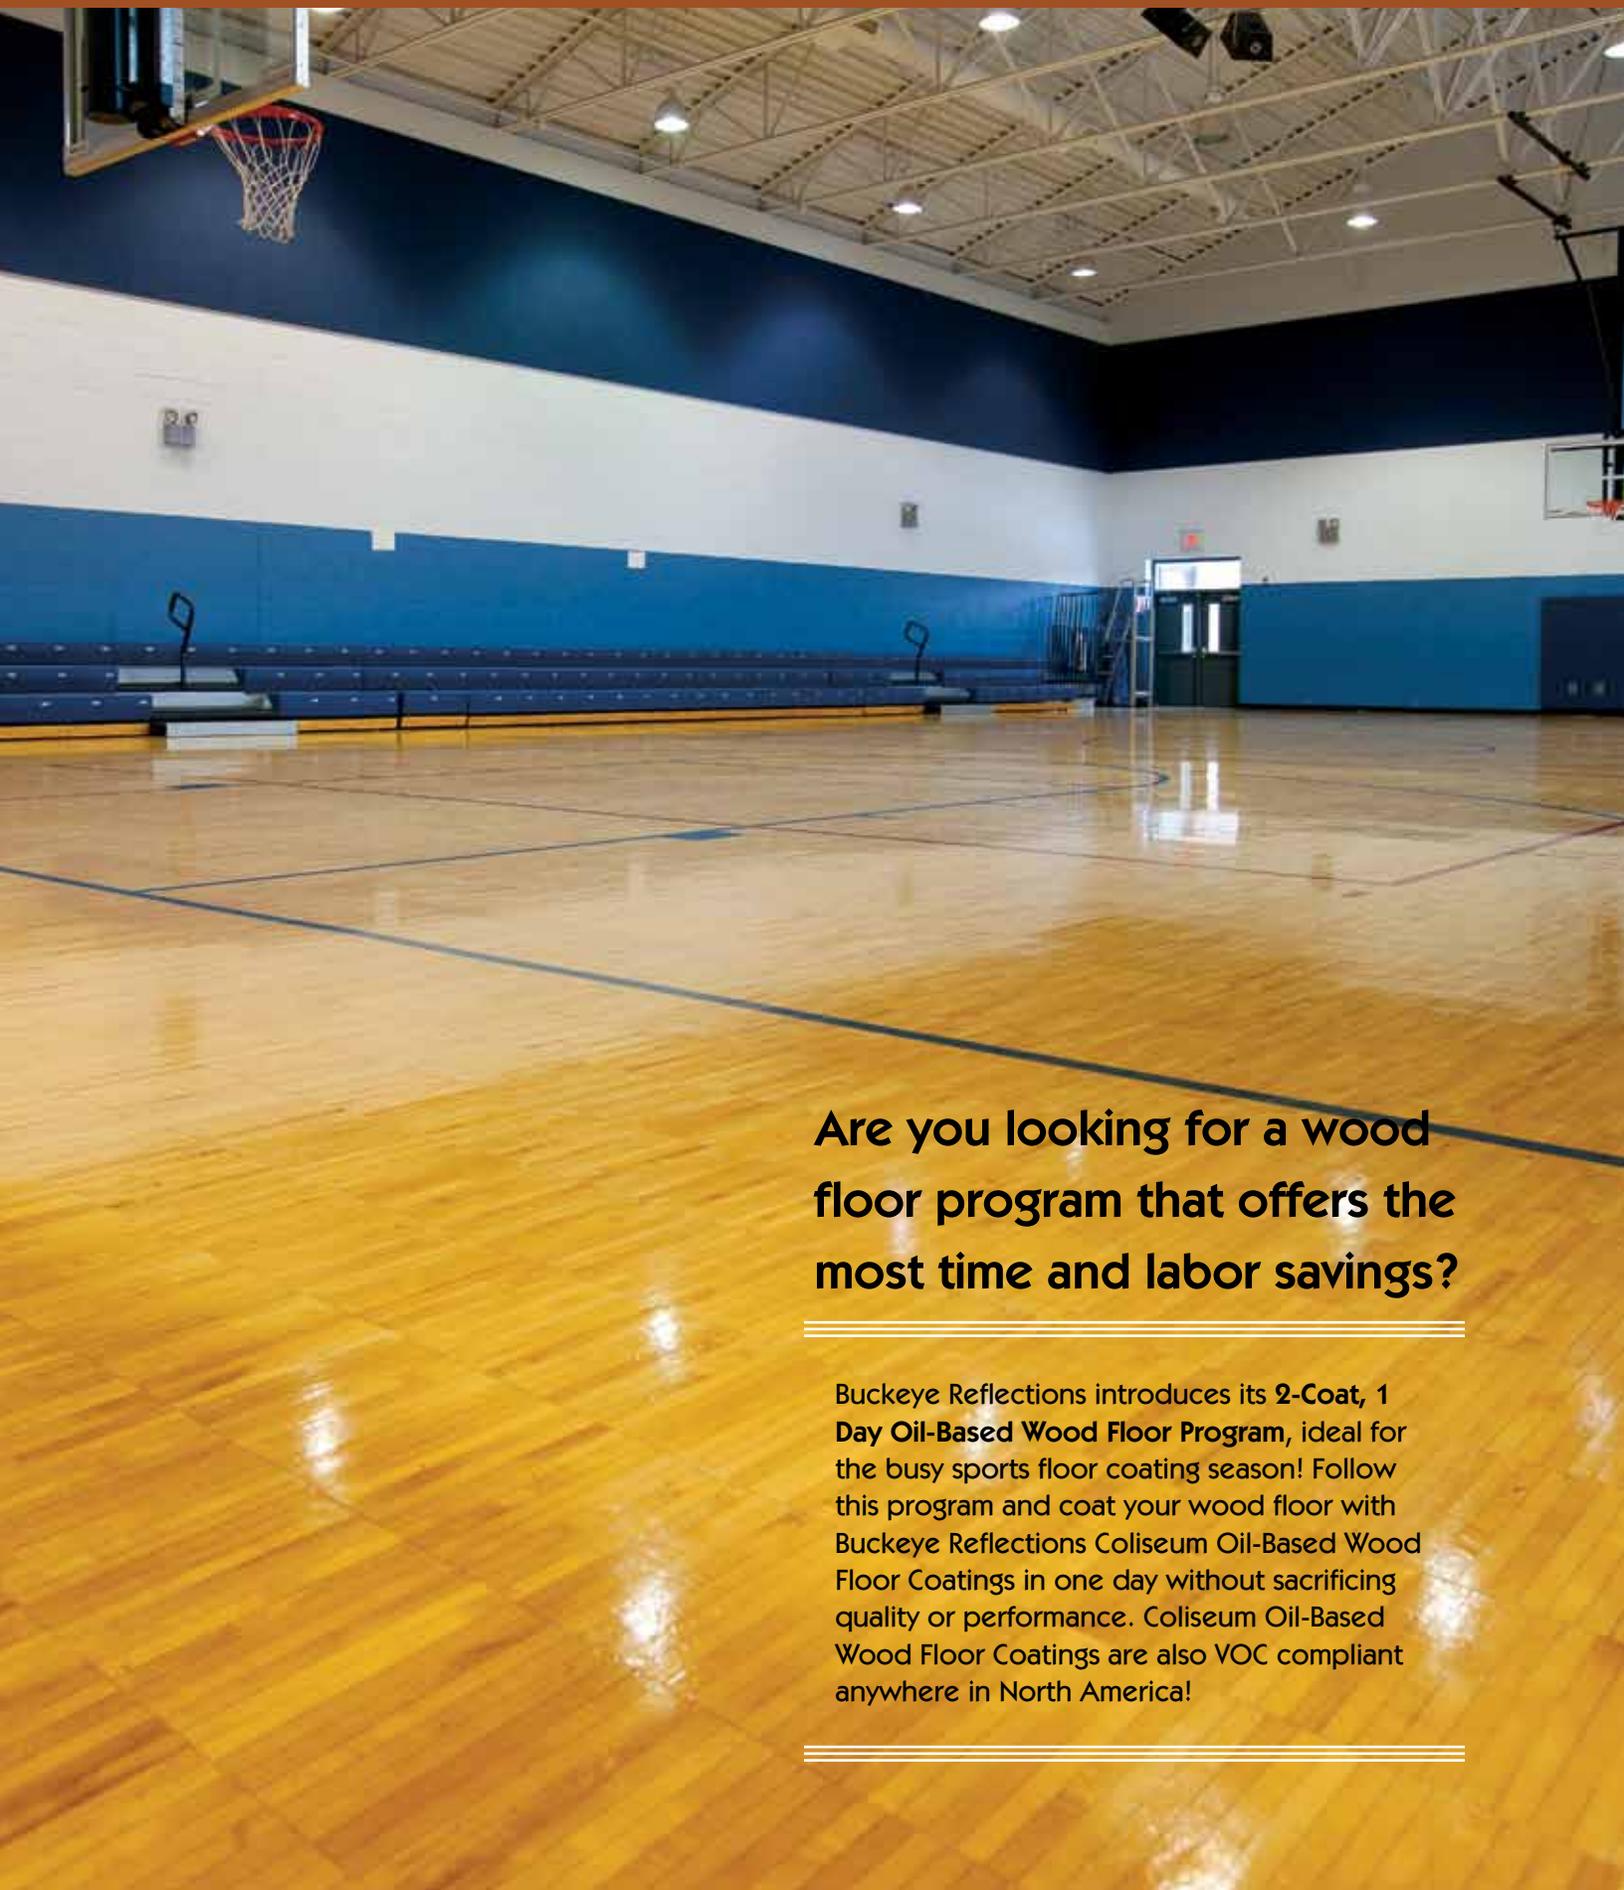

Are you looking for a wood floor program that offers the most time and labor savings?

Buckeye Reflections introduces its **2-Coat, 1 Day Oil-Based Wood Floor Program**, ideal for the busy sports floor coating season! Follow this program and coat your wood floor with Buckeye Reflections Coliseum Oil-Based Wood Floor Coatings in one day without sacrificing quality or performance. Coliseum Oil-Based Wood Floor Coatings are also VOC compliant anywhere in North America!

2-Coat, 1 Day Oil-Based Wood Floor Program

Wood Floor Preparation

1. Scrape off any tape, gum, or grime that is stuck on the floor using a putty knife.
**If there are bleachers, be sure and remove debris from behind them before you push them against the wall.*
2. Dust mop/sweep the entire floor thoroughly.

Dry Screening

1. Once floor is clean, lay out screens on entire gym floor, measuring out no more than 250 square feet per side. Position screens so you know when to flip another side or when to replace with a new screen.
**Buckeye Reflections recommends using #120 grit screens for most floors. For floors with excessive marks, you may use #100 grit screens*
2. **You must ONLY do a dry screen prep process** using a 20" buffing machine with a white synthetic buffing pad to hold your screen. Move along with the direction of the boards. After each 250 sq. ft. section is completed, promptly go against the boards in that section to ensure low spots have been correctly abraded.
3. After the floor is completely screened and there are no visible shiny spots, use a vacuum to remove heavy dust and tack the floor with **Coliseum Odorless, Virgin Mineral Spirits/Waterless Cleaner** until there is no dust left on the floor.

Wood Floor Coating Application

1. Once the floor is dry from the tack, apply 1 coat of **Coliseum™ 100** with **ONLY A HEAVYWEIGHT T-BAR** to ensure 400–500 sq. ft. coverage per gallon. Turn on HVAC system 1 hour after the first coat is applied to speed up the drying process.
**Coliseum 100 is a quick dry 350 VOC product. If anything other than a heavyweight T-bar is used, lap marks, puddles and/or ridging may occur.*
2. After 3-4 hours check the floor to make sure it is dry before you coat.
**Coliseum 100 dries in 3-5 hours. High humidity and/or extreme temperature conditions can lengthen drying times. Apply second coat within 10 hours. If second coat is not applied within 10 hours, buff with an in-between coat pad or SPP (Surface Preparation Pad) to achieve adhesion.*
3. Once first coat of **Coliseum 100** is completely dry, apply a second coat using **Coliseum™ 450, Coliseum 350** or **Larry's Super 40** depending on the VOC regulations.
4. Buckeye Reflections recommends applying coats with a heavy weight T-bar to get 500–600 sq. ft. coverage per gallon.
**If you prefer, you may apply these coatings with alternative application methods (EZ-Way, Wax-O-Matic, Multi-flo, etc.).*
5. After coats, lock all doors and allow 5 days before any floor use. Turn on the HVAC system 5 hours after the coating application to help dry the floor. Allow the HVAC system to remain on at a temperature between 65–80°F (18–27°C) for the remaining 5 days to ensure proper curing.

Get your gym floor to look from dull to shiny in one day!



Try our 2-Coat, 1 Day Oil-Based Wood Floor Program!



Buckeye International, Inc.

2700 Wagner Place • Maryland Heights • MO 63043 • USA
800.321.2583 • www.buckeyereflections.com